

TOOLOX® 33, 40 AND 44

ENGINEERING & TOOL STEEL

TYPICAL VALUES

Toolox® 33 - Mechanical Properties	-20°C	+20°C	+200°C	+300°C	+400°C	+500°C
Hardness (HBW)		300	305	290	270	
Hardness (HRC)		~29	~30	~29	~26	
Yield strength R _{p0.2} (MPa)		850	690	680	590	560
Tensile strength R _m (MPa)		980	900			
Elongation, A5, (%)		16	12			
Reduction of Area Z (%)		55				
Impact toughness, Charpy-V (J)	41	100	170	180	180	

Toolox® 40 - Mechanical Properties	-20°C	+20°C	+200°C	+300°C	+400°C	+500°C
Hardness (HBW)		400				
Hardness (HRC)		~40				
Yield strength R _{p0.2} (MPa)		1150	1010	990	900	780
Tensile strength R _m (MPa)		1260	1170	1160	1060	900
Elongation, A5, (%)		14	14	14	15	16
Impact toughness, Charpy-V (J)	18	38				

Toolox® 44 - Mechanical Properties	-20°C	+20°C	+200°C	+300°C	+400°C	+500°C
Hardness (HBW)		450	440	415	380	345
Hardness (HRC)		~45	~44	~42	~38	~35
Yield strength R _{p0.2} (MPa)		1300	1150	1040	980	825
Tensile strength R _m (MPa)		1450	1340	1270	1190	1010
Elongation, A5, (%)		13	10	12	14	19
Reduction of Area Z (%)		35				
Impact toughness, Charpy-V (J)	13	30	60	80	80	


Physical Properties	+20°C		+200°C		+400°C	
	Toolox® 33	Toolox® 44	Toolox® 33	Toolox® 44	Toolox® 33	Toolox® 44
Heat conductivity (W/m*K)	35	34	35	32	30	31
Thermal expansion coefficient (10 ⁻⁶ /K)	13.1	13.5	13.1	13.5	13.1	13.5

Inclusions			
	Toolox® 33	Toolox® 40	Toolox® 44
Inclusion size (equiv. diam.)	6 micron	6 micron	6 micron
Area fraction	0.015%	0.015%	0.015%
Aspect Ratio	1.2	1.2	1.2


Typical chemical composition	Toolox® 33	Toolox® 40	Toolox® 44
C	0.23%	0.28%	0.32%
Si	1.1%	1.1%	0.9%
Mn	0.8%	0.6%	0.8%
P	Max 0.011%	Max 0.011%	Max 0.011%
S	Max 0.003%	Max 0.002%	Max 0.003%
Cr	Max 1.60%	Max 1.30%	Max 1.70%
Mo	Max 0.80%	Max 1.10%	Max 1.40%
V	Max 0.12%	Max 0.12%	Max 0.17%
Ni	Max 1.0%	Max 1.4%	Max 1.4%
CEIIW	0.65 (Max 0.69)	0.80 (Max 0.84)	0.96 (Max 1.00)
CET	0.39 (Max 0.42)	0.47 (Max 0.50)	0.57 (Max 0.60)

SURFACE TECHNOLOGY


Gas nitriding of Toolox® 33

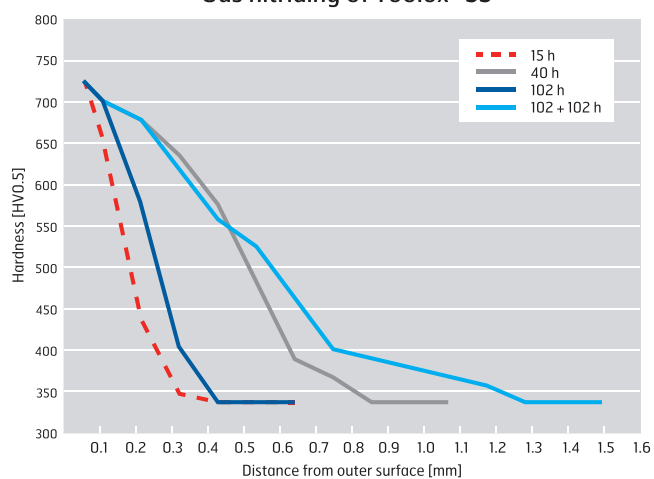

Gas nitriding of Toolox® 44

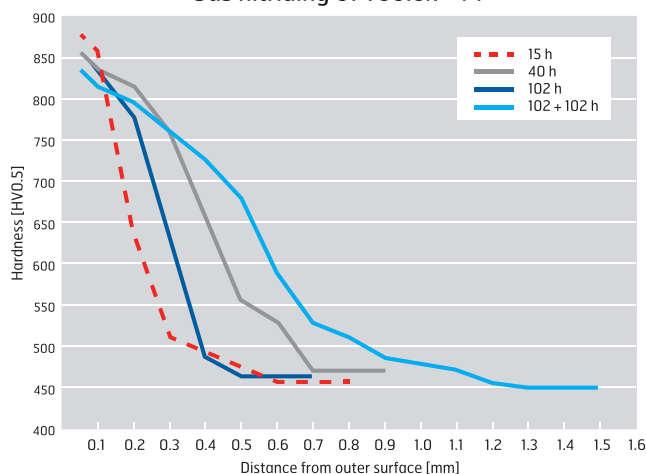

HARD & TOUGH

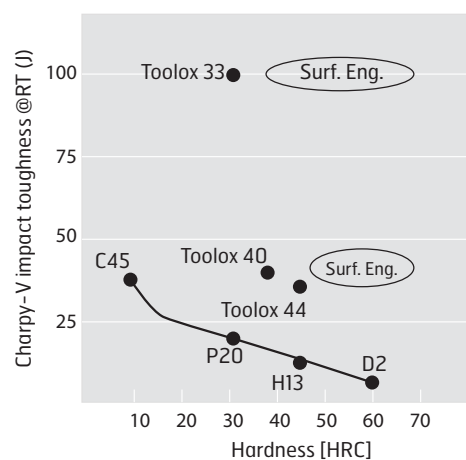

For more information concerning Toolox® products, please contact your local sales representative.


Find your local sales contact and other useful information with the SSAB app!



iPhone Android

www.ssab.com

Download by scanning the code or search for "SSAB" in your app store.

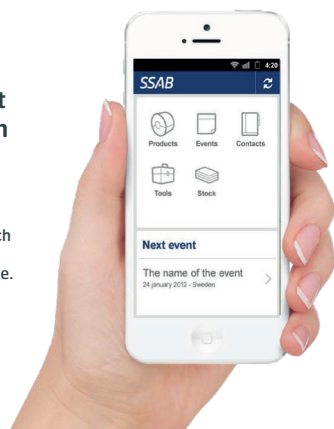

SSAB